

Spectral and Thermal Properties of Tm³⁺ Doped in ZincLithiumTungstenAntimonyBorophosphateGlasses

S.L.Meena

Ceramic Laboratory, Department of physics, Jai NarainVyas University, Jodhpur 342001(Raj.) India

Abstract

Glass sample of zinclithium tungstenantimonyborophosphate:

(45-x) P₂O₅:10ZnO:10Li₂O:10WO₃:10Sb₂O₃:15B₂O₃:xTm₂O₃. (where x=1,1.5 and 2 mol%) have been prepared by melt-quenching technique. The amorphous nature of the prepared glass samples was confirmed by X-ray diffraction. DTA curve was analysed to evaluate the glass transition temperature (T_g), onset crystallization temperature (T_c), melting temperature (T_m) and hence study the thermal properties. Optical absorption and fluorescence spectra were recorded at room temperature for all glass samples. Judd-Ofelt intensity parameters Ω_λ (λ=2, 4 and 6) are evaluated from the intensities of various absorption bands of optical absorption spectra. Using these intensity parameters various radiative properties like spontaneous emission probability, branching ratio, radiative life time and stimulated emission cross-section of various emission lines have been evaluated

Keywords: ZLTABP Glasses, Optical Properties, Judd-Ofelt Theory, Rare earth ions.

Date of Submission: 21-01-2024

Date of Acceptance: 31-01-2024

I. Introduction

Glass materials doped with rare earth ions are widely used mainly for optical devices, wave guide laser, sensors, up-conversion lasers, white light emitting diodes [1-5]. Glasses based on heavy metal oxide have received increased attention due to their manifold possible applications in the field of glass ceramics, layers for optoelectronics devices, thermal and mechanical sensors [6-10]. Phosphate glasses possess easier preparation, large transparency window, high refractive index, low phonon energy, better thermal stability, high density, good mechanical and chemical durability [11-14]. Phosphate glasses are promising laser hosts because they are able to accommodate higher content of rare earth ions and still remain amorphous in comparison with other glass systems. Due to their excellent thermal, physical and optical properties, they are used in fiber lasers, spectral conversion, photo-voltaic solar cells, temperature sensors and optical coherence tomography [15-17]. The addition of network modifier (NMF) Li₂O is to improve both electrical and mechanical properties of such glasses [18]. Phosphate glasses containing Tm³⁺ ions good for candidates because of their strong absorption and emission in the UV and visible spectral regions [19-21]. Recently Tm³⁺ ions doped glasses found important in the area of wave guide laser, laser action, solar cells and optical fibers [22-24].

The present work reports on the preparation and characterization of rare earth doped heavy metal oxide (HMO) glass systems for lasing materials. I have studied on the absorption, emission and thermal properties of Tm³⁺ doped zinc lithium tungsten antimony borophosphate glasses. The intensities of the transitions for the rare earth ions have been estimated successfully using the Judd-Ofelt theory. The laser parameters such as radiative probabilities (A), branching ratio (β), radiative life time (τ_R) and stimulated emission cross section (σ_p) are evaluated using J.O. intensity parameters (Ω_λ, λ=2, 4 and 6).

II. Experimental Techniques

Preparation of glasses

The following Tm³⁺ doped borophosphate glass samples (45-x) P₂O₅:10ZnO:10Li₂O:10WO₃:10Sb₂O₃:15B₂O₃:xTm₂O₃. (where x=1,1.5 and 2 mol%) have been prepared by melt-quenching method. Analytical reagent grade chemical used in the present study consist of P₂O₅, ZnO, Li₂O, WO₃, Sb₂O₃, B₂O₃ and Tm₂O₃. They were thoroughly mixed by using an agate pestle mortar. then melted at 1070°C by an electrical muffle furnace for 2h., After complete melting, the melts were quickly poured in to a preheated stainless steel mould and annealed at temperature of 250°C for 2h to remove thermal strains and stresses. Every time fine powder of cerium oxide was used for polishing the samples. The glass samples so prepared were of good optical quality and were transparent. The chemical compositions of the glasses with the name of samples are summarized in

Table 1.**Table 1.**

Chemical composition of the glasses

| Sample | Glass composition (mol %) |
|----------------|--|
| ZLTABP (UD) | 45 P ₂ O ₅ :10ZnO:10Li ₂ O:10WO ₃ :10Sb ₂ O ₃ :15B ₂ O ₃ |
| ZLTABP (TM1) | 44 P ₂ O ₅ :10ZnO:10Li ₂ O:10WO ₃ :10Sb ₂ O ₃ :15B ₂ O ₃ :1Tm ₂ O ₃ |
| ZLTABP (TM1.5) | 43.5 P ₂ O ₅ :10ZnO:10Li ₂ O:10WO ₃ :10Sb ₂ O ₃ :15B ₂ O ₃ :1.5 Tm ₂ O ₃ |
| ZLTABP (TM2) | 43 P ₂ O ₅ :10ZnO:10Li ₂ O:10WO ₃ :10Sb ₂ O ₃ :15B ₂ O ₃ :2Tm ₂ O ₃ |

ZLTABP (UD) -Represents undoped Zinc Lithium Tungsten Antimony Borophosphate glass specimen.

ZLTABP (TM) -Represents Tm³⁺ doped Zinc Lithium Tungsten Antimony Borophosphate glass specimens.

III. Theory

Oscillator Strength

The intensity of spectral lines are expressed in terms of oscillator strengths using the relation [25].

$$f_{\text{expt.}} = 4.318 \times 10^{-9} \int \varepsilon(\nu) d\nu \quad (1)$$

where, $\varepsilon(\nu)$ is molar absorption coefficient at a given energy ν (cm⁻¹), to be evaluated from Beer–Lambert law.

Under Gaussian Approximation, using Beer–Lambert law, the observed oscillator strengths of the absorption bands have been experimentally calculated [26], using the modified relation:

$$P_m = 4.6 \times 10^{-9} \times \frac{1}{cl} \log \frac{I_0}{I} \times \Delta\nu_{1/2} \quad (2)$$

where c is the molar concentration of the absorbing ion per unit volume, l is the optical path length, $\log I_0/I$ is optical density and $\Delta\nu_{1/2}$ is half band width.

Judd-Ofelt Intensity Parameters

According to Judd [27] and Ofelt [28] theory, independently derived expression for the oscillator strength of the induced forced electric dipole transitions between an initial J manifold $|4f^N(S, L) J\rangle$ level and the terminal J' manifold $|4f^N(S', L') J'\rangle$ is given by:

$$\frac{8\pi^2 mc \bar{\nu}}{3h(2J+1)n} \frac{1}{n} \left[\frac{(n^2+2)^2}{9} \right] \times S(J, J') \quad (3)$$

Where, the line strength $S(J, J')$ is given by the equation

$$S(S', L') = e^2 \sum_{\lambda=2,4,6} \Omega_{\lambda} \langle 4f^N(S, L) J \| U^{(\lambda)} \| 4f^N(S', L') J' \rangle^2 \quad (4)$$

In the above equation m is the mass of an electron, c is the velocity of light, ν is the wave number of the transition, h is Planck's constant, n is the refractive index, J and J' are the total angular momentum of the initial and final level respectively, Ω_{λ} ($\lambda=2,4$ and 6) are known as Judd-Ofelt intensity parameters.

Radiative Properties

The Ω_{λ} parameters obtained using the absorption spectral results have been used to predict radiative properties such as spontaneous emission probability (A) and radiative life time (τ_R), and laser parameters like fluorescence branching ratio (β_R) and stimulated emission cross section (σ_p).The spontaneous emission probability from initial manifold $|4f^N(S', L') J'\rangle$ to a final manifold $|4f^N(S, L) J\rangle$ is given by:

$$A[(S', L') J'; (S, L) J] = \frac{64 \pi^2 \nu^3}{3h(2J'+1)} \left[\frac{n(n^2+2)^2}{9} \right] \times S(J', J) \quad (5)$$

Where, $S(J', J) = e^2 [\Omega_2 \| U^{(2)} \|^2 + \Omega_4 \| U^{(4)} \|^2 + \Omega_6 \| U^{(6)} \|^2]$ The fluorescence branching ratio for the transitions originating from a specific initial manifold $|4f^N(S', L') J'\rangle$ to a final many fold $|4f^N(S, L) J\rangle$ is given by

$$\beta [(S', L') J'; (S, L) J] = \frac{A[(S', L') J']}{A[(S', L') J'; (S, L) J]} \quad (6)$$

where, the sum is over all terminal manifolds.

The radiative life time is given by

$$\tau_{rad} = \frac{1}{\sum_{S, L, J} A[(S', L') J'; (S, L) J]} \quad (7)$$

where, the sum is over all possible terminal manifolds. The stimulated emission cross-section for a transition from an initial manifold $|4f^N (S', L') J\rangle$ to a final manifold $|4f^N (S, L) J\rangle$ is expressed as

$$\sigma_p(\lambda_p) = \left[\frac{\lambda_p^4}{8\pi c n^2 \Delta\lambda_{eff}} \right] \times A[(S', L') J'; (\bar{S}, \bar{L}) \bar{J}] \quad (8)$$

where, λ_p the peak fluorescence wavelength of the emission band and $\Delta\lambda_{eff}$ is the effective fluorescence line width.

IV. Result and Discussion

XRD Measurement

Figure 1 presents the XRD pattern of the sample contain - P₂O₅ which is show no sharp Bragg's peak, but only a broad diffuse hump around low angle region. This is the clear indication of amorphous nature within the resolution limit of XRD instrument

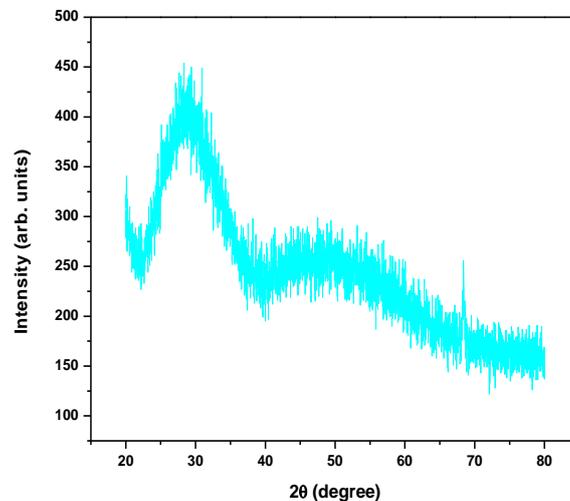


Fig. 1 X-ray diffraction pattern of ZLTABP TM (01) glass.

Thermal Property

Differential thermal analysis checks the heat absorbed by glass samples during heating or cooling. Fig. 2 depicts the DTA thermogram of powdered ZLTABP sample. The glass transition temperature (T_g), onset crystallization temperature (T_c), crystallization temperature (T_p), melting temperature (T_m), thermal stability (T_s), thermal stability parameter (S), Hurbe's criterion (H_r) and reduced glass transition temperature (T_{rg}) were calculated. All the determined thermal parameters are given in table 2.

| Glass samples | T_g (°C) | T_c (°C) | T_p (°C) | T_m (°C) | T_s (°C) | H_r (°C) | S (°C) | T_{rg} (°C) |
|-----------------|------------|------------|------------|------------|------------|------------|----------|---------------|
| ZLTABP TM (01) | 374 | 505 | 546 | 682 | 131 | 0.232 | 14.36 | 0.548 |
| ZLTABP TM (1.5) | 376 | 506 | 548 | 685 | 130 | 0.235 | 14.52 | 0.549 |
| ZLTABP TM (02) | 377 | 508 | 550 | 688 | 131 | 0.244 | 13.90 | 0.548 |

The thermal stability of the glass samples can be calculated by difference between onset crystallization temperature and transition temperature [29].

$$\text{Thermal stability } (T_s) = T_c - T_g \quad (9)$$

Hruby's criterion is calculated using the Hurby's relation [30].

$$\text{Hruby's criterion } (H_r) = [(T_p - T_c) / (T_m - T_c)] \quad (10)$$

Reduced glass transition temperature is given as [31].

$$\text{Reduced glass transition temperature } (T_{rg}) = T_g / T_m \quad (11)$$

Thermal stability parameter can be calculated using [32].

$$\text{Thermal stability parameter } (S) = [(T_p - T_c) \times (T_c - T_g)] / T_g \quad (12)$$

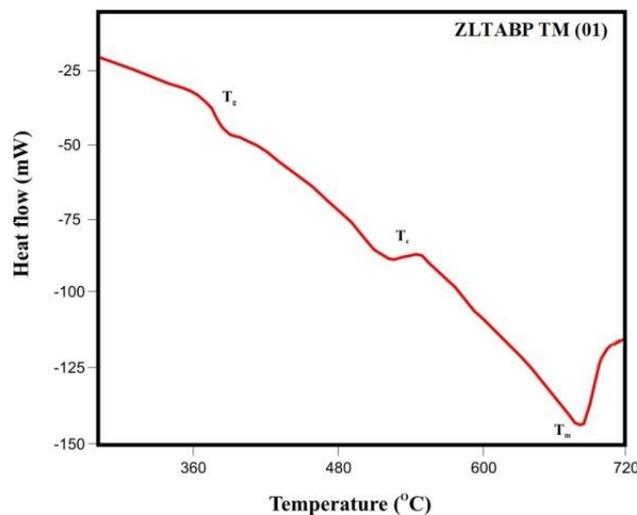


Fig.2: DTA curve of ZLTABP TM (01) glass.

Absorption Spectrum

The absorption spectra of Tm³⁺ doped ZLTABP glass specimens have been presented in Figure 3 in terms of optical density versus wavelength. Five absorption bands have been observed from the ground state ³H₆ to excited states ³F₄, ³H₅, ³H₄, ³F₃ and ¹G₄ for ZLTABPTM(01) glass.

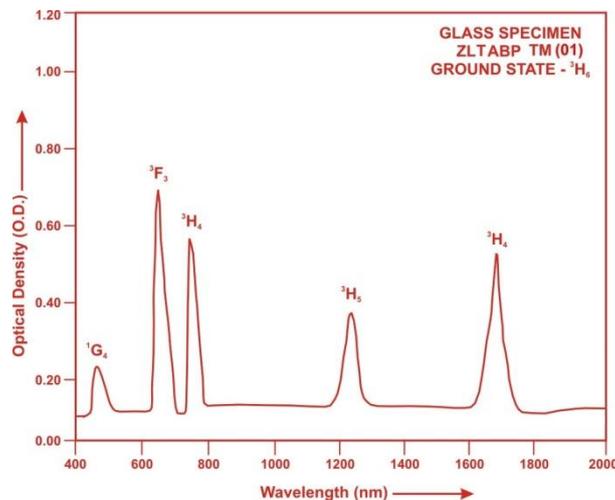


Fig. (3) Absorption spectrum of ZLTABP TM (01) glass.

The experimental and calculated oscillator strength for Tm³⁺ ions in ZLTABP glasses are given in **Table 3**.

Table 3: Measured and calculated oscillator strength ($P_m \times 10^{+6}$) of Tm³⁺ ions in ZLTABP glasses.

| Energy level from ³ H ₆ | Glass ZLTABP(TM01) | | Glass ZLTABP(TM1.5) | | Glass ZLTABP(TM02) | |
|---|--------------------|-------------------|---------------------|-------------------|--------------------|-------------------|
| | P _{exp.} | P _{cal.} | P _{exp.} | P _{cal.} | P _{exp.} | P _{cal.} |
| ³ F ₄ | 1.89 | 1.91 | 1.88 | 1.91 | 1.85 | 1.88 |
| ³ H ₅ | 1.50 | 1.50 | 1.48 | 1.49 | 1.46 | 1.49 |
| ³ H ₄ | 2.07 | 2.13 | 2.06 | 2.13 | 2.04 | 2.12 |
| ³ F ₃ | 3.06 | 3.13 | 3.04 | 3.12 | 3.02 | 3.11 |
| ¹ G ₄ | 0.84 | 0.92 | 0.82 | 0.92 | 0.80 | 0.92 |
| r.m.s. deviation | 0.0565 | | 0.0654 | | 0.0770 | |

In the zinc lithium tungsten antimony borophosphate glasses Ω_2 , Ω_4 and Ω_6 parameters decrease with the increase of x from 1 to 2 mol%. The order of magnitude of Judd-Ofelt intensity parameters is $\Omega_4 > \Omega_2 > \Omega_6$ for all the glass specimens. The spectroscopic quality factor (Ω_4 / Ω_6) related with the rigidity of the glass system has been found to lie between 1.436 and 1.444 in the present glasses. The values of Judd-Ofelt intensity parameters are given in **Table 4**.

Table 4: Judd-Ofelt intensity parameters for Tm³⁺ doped ZLTABP glass specimens.

| Glass Specimen | $\Omega_2(\text{pm}^2)$ | $\Omega_4(\text{pm}^2)$ | $\Omega_6(\text{pm}^2)$ | Ω_4 / Ω_6 |
|-----------------|-------------------------|-------------------------|-------------------------|-----------------------|
| ZLTABP (TM 01) | 7.170 | 8.771 | 6.076 | 1.444 |
| ZLTABP (TM 1.5) | 7.203 | 8.699 | 6.056 | 1.436 |
| ZLTABP (TM 02) | 7.083 | 8.566 | 6.070 | 1.411 |

Fluorescence Spectrum

The fluorescence spectrum of ZLTABP TM (01) doped in zinc lithium tungsten antimony borophosphate glass is shown in Figure 4. There are nine broad bands observed in the Fluorescence spectrum of Tm³⁺ doped zinc lithium tungsten antimony borophosphate glass. The wavelengths of these bands along with their assignments are given in Table 5. The peak with maximum emission intensity appears at 1810nm and corresponds to the (³F₄ → ³H₆) transition.

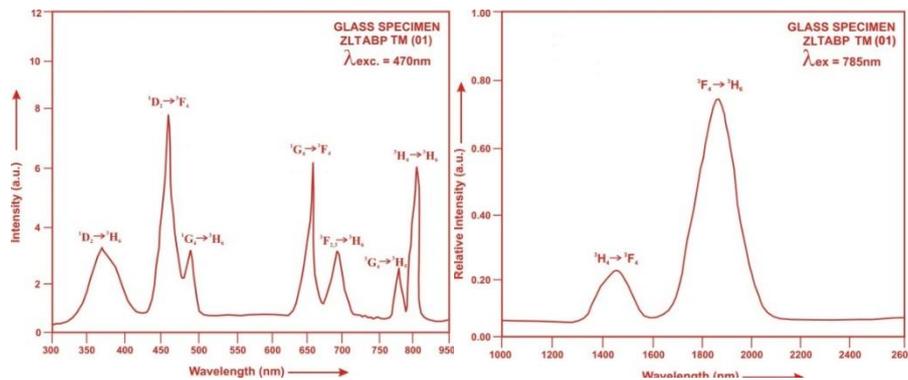


Fig. (4). Fluorescence spectrum of ZLTABP TM (01) glass.

Table 5: Emission peak wave lengths (λ_p), radiative transition probability (A_{rad}), branching ratio (β), stimulated emission cross-section (σ_p) and radiative life time (τ_R) for various transitions in Tm³⁺ doped ZLTABP glasses

| Transition | ZLTABP (TM 01) | | | | | ZLTABP (TM 1.5) | | | | | ZLTABP (TM 02) | | | | |
|---|--------------------|-------------------|---------|---------------------------|-----------------|-------------------|---------|---------------------------|-----------------|-------------------|----------------|---------------------------|-----------------|--|--|
| | $\lambda_{em}(nm)$ | $A_{rad}(s^{-1})$ | β | $\sigma_p(10^{-20} cm^2)$ | $\tau_R(\mu s)$ | $A_{rad}(s^{-1})$ | β | $\sigma_p(10^{-20} cm^2)$ | $\tau_R(\mu s)$ | $A_{rad}(s^{-1})$ | β | $\sigma_p(10^{-20} cm^2)$ | $\tau_R(\mu s)$ | | |
| ¹ D ₂ → ³ H ₆ | 365 | 54163.00 | 0.6284 | 1.517 | 11.6027 | 53909.90 | 0.6270 | 1.538 | 11.6311 | 53491.70 | 0.6274 | 1.555 | 11.7293 | | |
| ¹ D ₂ → ³ F ₄ | 455 | 17730.30 | 0.2057 | 2.353 | | 17794.20 | 0.2070 | 2.454 | | 17545.68 | 0.2058 | 2.483 | | | |
| ¹ G ₂ → ³ H ₆ | 480 | 2235.42 | 0.0259 | 0.555 | 2232.85 | 0.0260 | 0.587 | 2205.01 | 0.0259 | 0.617 | | | | | |
| ¹ G ₂ → ³ F ₄ | 651 | 734.31 | 0.0085 | 1.425 | 732.33 | 0.0085 | 1.558 | 731.81 | 0.0086 | 1.677 | | | | | |
| ³ F _{3,3} → ³ H ₆ | 689 | 5552.59 | 0.0644 | 2.358 | 5535.85 | 0.0644 | 2.433 | 5525.78 | 0.0648 | 2.495 | | | | | |
| ¹ G ₂ → ³ H ₄ | 785 | 2137.96 | 0.0248 | 2.482 | 2137.38 | 0.0249 | 2.593 | 2139.77 | 0.0251 | 2.646 | | | | | |
| ³ H ₁ → ³ H ₆ | 798 | 2821.69 | 0.0327 | 4.350 | 2823.03 | 0.0328 | 4.558 | 2814.10 | 0.0330 | 4.690 | | | | | |
| ³ H ₁ → ³ F ₄ | 1450 | 359.63 | 0.0042 | 3.826 | 359.35 | 0.0042 | 3.915 | 356.82 | 0.0042 | 4.005 | | | | | |
| ³ F ₄ → ³ H ₆ | 1810 | 451.84 | 0.0052 | 7.299 | 451.22 | 0.0052 | 7.394 | 446.01 | 0.0052 | 7.513 | | | | | |

V. Conclusion

In the present study, the glass samples of composition (45-x) P₂O₅:10ZnO:10Li₂O:10WO₃:10Sb₂O₃:15B₂O₃:xTm₂O₃ (where x =1, 1.5 and 2mol %) have been prepared by melt-quenching method. The value of stimulated emission cross-section (σ_p) is found to be maximum for the transition (³F₄→³H₆) for glass ZLTABP (TM 02), suggesting that glass ZLTABP (TM 02) is better compared to the other two glass systems ZLTABP (TM 01) and ZLTABP (TM 1.5). The prepared glass samples have good thermal stability as specified by calculated glass stability factors and therefore, these samples can be good materials for fiber fabrication.

References

- [1]. Ding, Dashuang, Gao,J.,Zhang,S.,Duo, L.(2020). The Photoluminescence Properties Of Pr³⁺-Yb³⁺ Co-Doped Gallo-Germanate Glasses And Glass Ceramics As Energy Converter.J.Lumin.226,117512.
- [2]. Vighnesh,K.R.,Ramya, B.,Nimitha, S.,Wagh, A.,Sayyed,M.I.,Sakar, E.,Yakout, H.A. And Dahshan, A.(2020). Structural, Optical, Thermal, Mechanical, Morphological And Radiation Shielding Parameters Of Pr³⁺Doped Zaifb Glass Systems, Optical Materials 99,109512.
- [3]. Damodaraiah, S.,Prasad, V. R.,Lakshmi, R.P.V.AndRatnakaram, Y.C.(2019). Luminescence Behaviour And Phonon Sideband Analysis Of Europium Doped Bi₂O₃ Based Phosphate Glasses For Red Emitting Device Applications, Opt. Mat. 92, 352-358.
- [4]. Kaur, R., Khanna,A.(2020).Photoluminescence And Thermal Properties Of Trivalent Ion-Doped Lanthanum Tellurite Anti- Glass Composite Samples, J. Lum., 225, 117375.
- [5]. Meena, S.L.(2022).Spectral And Raman Analysis Of Eu³⁺Doped In Zinc Lithium Cadmium Magnesium Borophosphate Glasses,Iosr Journal Of Applied Physics,14,39-44.
- [6]. Monisha, M., Nancy, A., Souza, D., Legde, V., Prabhu, N.S. And Sayyed, M.I.(2020).Dy³⁺ Doped SiO₂- B₂O₃-Al₂O₃-NaF-ZnF₂ Glasses , An Exploration Of Optical And Gamma Radiation Shielding Features, Current Applied Physics 20(11), 1207-1210.
- [7]. Deepa, A. V. ,Murygasen, P., Muralimanohar, P., Sathyamoorthy, K., Kumar, P. V.(2019). A Comparison On The Structural And Optical Properties Of Different Rare Earth Doped Phosphate Glass, Optik, 181,361-367.
- [8]. Hongisto, M., Vebar, A., Botti,N.G., Danto, S.,Juberá,V.AndPetita,L.(2020).Transparent Yb³⁺ Doped Phosphate Glass Ceramics, Ceramics International 46(16),26317-26325.
- [9]. Wu, T.,Cheng, Y., Zhong, H.,Peng, H. And Hu, J.(2018). Thermal Stability And Spectral Properties Of Tm³⁺,Yb³⁺Coped Tellurite Glasses. Glass Phys. Chem., 44, 163–169.
- [10]. Meena, S.L.(2021).Spectral And Raman Analysis Properties Of Pr³⁺ Doped Zinc Lithium Sodium Alumino Bismuth Borate Glasses,Int.Phys-Appl.Sci.8,1-10.
- [11]. Dousti, M.R. , Poirier, G.Y. And De Camargo, A.S.S.(2020).Tungsten Sodium Phosphate Glasses Doped With Trivalent Rare Earth Ions (Eu³⁺, Tb³⁺, Nd³⁺, Er³⁺) For Visible And Near Infrared Applications, Journal Of Non- Cryst. Solids 530, 119838.
- [12]. Bentouil,O.,Aiadi,K.E.,Rehouma,F.,Poulain, M.(2013). Spectroscopic Studies Of Rare Earth-Doped Halogeno-Phosphate Glasses, J.Opt.Adv.Mat.15, 1204-1208.
- [13]. Deedwaniya, P.,Meena, S.L.(2022).Spectroscopic Properties Of Er³⁺ Doped Zinc Lithium Calcium Potassiumniobate Phosphate Glasses,Int.J.Res.Appl.Sci.Eng.Tech.10,320-325.
- [14]. Shikerkar, A.G., Desa, J.A.E., Krishna, P.S.R. And Chitr, R.(2000).Diffraction Studies Of Rare Earth Phosphate Glasses, J. Non-Cryst. Solids,270,234- 246.
- [15]. Meena. S.L. (2021).Spectral And Transmittance Properties Of Er³⁺ Doped Zinc Lithium Lead Calcium Borophosphate Glasses,Int.J.Res.Appl.Sci.Eng.Tech.9,636-643.
- [16]. Moorthy,L.R.,Rao,T.S.,Janardhanam,K.,Radhapathy,K.(2000).Optical Absorption And Emission Properties Of Pr(III) In Alkali Chloroborophosphate Glasses,J.Alloys-Comp.298,59-67.
- [17]. Ansari,S.A.,Ansari,M.O.,Alshahrie,A.,Shahadat,M.,Parveen,N.,Darwesh,R.,Aboushoushah,S.F.(2022).Concentrationdependent Improved Spectroscopic Characteristics And Near White Light Emission In Borophosphate Glasses Doped With Holmium,Appl.Sci.12,2632.
- [18]. Weber, M.J. (1990). Science And Technology Of Laser Glass. J. Non-Cryst. Solids, 123, 208–222.
- [19]. Han,L.,Song,J.,Liu,W.,Xiao,Z.,Zhang,L.,Lu,A.,Xiao,Z.,You,W.,Zhang,Q.(2020).Preparation And Luminescent Properties Of Tm³⁺-Dy³⁺ Co-Doped Phosphate Glass For White Light –Emitting-Diode Applications,227,117559.
- [20]. Zhong,H.J.,Chen,G.H.,Yao,L.Q.,Wang,J.X.,Yang,Y.,Zhang,R.(2015).The White Light Emission Properties Of Tm³⁺/Tb³⁺/Sm³⁺ Triply Doped Sro-Zno-P2o5 Glass, J. Non-Cryst. Solids 427, 10-15.
- [21]. Chen,Y.,Chen,G.H.,Liu,X.Y.,Yuan,C.L.,Zhou,C.R.(2017).Tunable,Luminescence Mediated By Energy Transfer In Tm³⁺/Dy³⁺ Co-Doped Phosphate Glasses Under Uv Excitation,Opt.Mater.73,535-540.
- [22]. Liu,X.Y.,Chen,G.H.,Chen,Y.,Xu,J.W.(2018).Luminescent Properties And Energy Transfer Of Tm³⁺/Dy³⁺ Co-Doped Oxyfluoride Borate Glasses For White Leds,J.Mater.Sci.Mater.Electron,29,16041-16049.
- [23]. Yasukevich,A.S.,Rachkovskaya,G.E.,Zakharevich,G.B.,Trusova,E.E.,Kornienko,A.A.,Dunina,E.B.,Kisel,V.E.,Kuleshov,N.V.(2021).Spectral-Luminescence Properties Of Oxyfluoride Lead-Silicate-Germanate Glass Doped With Tm³⁺ Ions,J.Lumin.229,117667.
- [24]. Lalla,E.A.,Konstantinidis,M.,De Souza,I.,Daly,M.G.,Martin,I.R.,Lavin,V.,Rodriguez-Mendoza,U.R.(2020).Judd-Ofelt Parameters Of Re³⁺-Doped Flurotellurite Glass(Re³⁺=Pr³⁺,Nd³⁺,Sm³⁺,Tb³⁺,Dy³⁺,Ho³⁺,Er³⁺ And Tm³⁺), J. Alloys Compd.845,156028.
- [25]. Gorrler-Walrand, C. And Binnemans, K. (1988). Spectral Intensities Of F-F Transition. In: Gshneider Jr., K.A. And Eyring, L., Eds., Handbook On The Physics And Chemistry Of Rare Earths, Vol. 25, Chap. 167, North-Holland, Amsterdam, 101.
- [26]. Sharma, Y.K., Surana, S.S.L. And Singh, R.K. (2009). Spectroscopic Investigations And Luminescence Spectra Of Sm³⁺ Doped Soda Lime Silicate Glasses. Journal Of Rare Earths, 27, 773.
- [27]. Judd, B.R. (1962). Optical Absorption Intensities Of Rare Earth Ions. Physical Review, 127, 750.
- [28]. Ofelt, G.S. (1962). Intensities Of Crystal Spectra Of Rare Earth Ions. The Journal Of Chemical Physics, 37, 511.
- [29]. Karthikeyan,B.,Mohan,S.(2003).Structural,Optical And Glass Transition Studies On Nd³⁺ Doped Lead Bismuth Borate Glasses,Phys.B.334,298-302.
- [30]. Hurby,A.(1972).Evaluation Of Glass –Forming Tendency By Means Of Dta.Czech.J.Phys.B.22,1187-1193.
- [31]. Kumar, V.Sharma,S.,Pandey,O.P.,Singh,K.(2010).Thermal And Physical Properties Of 30sro-40sio2-20b2o3-10a2o3(A=La,Y,Al) Glasses And Their Chemical Reaction With Bismuth Vanadate For Sofc.Solid State Ionic,181,79-85.
- [32]. Shwetha,M.,Eraiah,B.(2019).Influence Of Er³⁺ Ions On The Physical,Structural,Optical And Thermal Properties Of Zno-Li2o-P2o5 Glasses, Appl.Phys.221,1-11.