

Effect of the blending between upland and combing waste on cotton fiber and yarn quality

Eman Rashwan El – Sayed¹ and Abo Baker E.M .Gadalla²

1. Spinning Research Department, Cotton Research Institute, Agricultural Research Center, Giza, Egypt

2. Fiber Research Department, Cotton Research Institute, Agricultural Research Center, Giza, Egypt

*Corresponding author: emanrashwan28@gmail.com

Abstract

Blending of cotton wastes with raw materials to produce different textile products has economically and environmentally beneficial. This study was carried out in Cotton Research Institute, Agricultural Research Center. This investigation aimed to study the impact of blending ratio on fiber, mechanical and physical yarn quality properties to find out the optimum blending ratio that achieves the optimum yarn quality properties. For this purpose, fiber properties, mechanical and physical yarn quality properties of ring spun yarns produced from cotton variety Giza95, Delta pine245 cotton variety (upland cotton) combed cotton waste of Extra Fine Giza93 and six different binary blend ratios were studied. Blended samples were spun into 36s, and 40s, carded yarns at constant twist multiplier 4 on ring spinning system. the results showed that fiber properties, Physical and mechanical properties of yarns produced from Giza95 were better than 100% upland cotton, 100% combed cotton waste and the other blended yarns. 65% Giza95-35% combed waste of blended samples recorded higher fiber properties (maturity ratio, fiber length, uniformity index, fiber strength and fiber elongation) than all blended samples. Also, the same blended ratio at 36s, yarn count give betterlea count product strength, yarn strength, yarn elongation, evenness, imperfections and yarn hairiness compared with all blended yarns followed by 65% combed waste - 35% Giza95. While, the lowest yarn quality properties recorded by the blended yarn of 35% Giza95-65% Delta pine245. Also, it observed that increasing proportion of G95 cotton variety in blended samples led to improve fiber, mechanical and physical yarn properties.

Key words: Combed waste, Upland cotton, ring spinning, blending ratios

Date of Submission: 26-08-2022

Date of Acceptance: 10-09-2022

I. Introduction

Cotton is one of the best natural fibers in the world. It is one of the most important sources of national income in Egypt. Egyptian cotton has international reputation because it has unique physical and mechanical quality properties such as comfortable soft hand moisture absorbency, good strength, easy to handle and sew, drapes well, prints well and surface characteristics. Besides, it compatibility with other natural and synthetic fibers. (Saha et al.2020).The textile industry in Egypt faces great challenges for example it providing raw material of cotton at a cheap price to produce medium and coarse yarns for domestic market, competition in textile world and expert fine and extra fine yarns to international market (Mohamed et al. 2005).

The increase in population, the prices of raw materials, the demand for textile products, the decrease in agricultural areas and the lack of natural fibers led to an increase in the production costs in textile industry. The increase in both of textile production and consumption rate of raw materials led to huge amount of textile wastes. Textile industry wastes are generated in the various manufacturing processes of fibers, yarns, fabrics and garments (Wang 2010).

Disposing of textile wastes by burning it or dumping in landfills has negative effects on the environment. The best solution to this problem is reuse textile wastes to produce cheap textile products with acceptable quality properties. Recycling textile wastes has economic and environmental benefits. In addition, it reduces the amount of natural raw materials which used in textile industry, and reduces air, water and land pollutions. Also, recycling waste increases profitability (Bhatia et al 2014; Shama and Joel 2017).

There are no fibers have all the desirable properties. However, all fibers are poor in some properties so blending process of different types of fibers is practiced to improve the quality properties of yarn by combining desirable properties of constituent fibers and to reduce the cost (Langenhove2002; Bhardwaj and Juneja 2012).

In general, blending process is reduced production costs by blending expensive fibers with a cheaper fibers one. Furthermore, it is improved different yarn quality properties, combining desirable physical properties of both fiber components in the blended yarns, Color and appearance, where novel designs may be carried out by incorporating multi-color effects (Charankar et al.2007).

Mechanical and physical properties of blend yarns depend on quality properties of fiber of each component and their proportions in blended yarns (Rajalakshmi et al. 2012). increasing combed cotton waste and carded cotton waste for Giza90 cotton variety in blended led to decrease in fiber length, fiber strength, fiber and yarn elongation .While, micronaire value, yarn strength, yarn evenness and yarn imperfections increased (Mabrouk and Nour 2005).

(Cierpucha et al.2006) found that cotton yarns gave high yarn strength and low unevenness compared to blended yarns.

Blending cotton fibers and cotton wastes from ginning process with three blending ratios led to reduce production costs and improved most physical properties of blended yarns (Marinus 2007).

(Khan et al. 2015) reported that single yarn strength increased with increasing the proportion of pure cotton in the blended yarns. (Rizk et al. 2016) imported that upland cottons are lower fiber quality properties than Egyptian cotton. Therefore, blending upland cottons with Egyptian cottons improves mechanical and physical quality properties of blended yarns compared to upland cotton yarns and it reduces production costs.

Lint grade fully good fair of Giza 90 was blended with card waste and fibers from recycled fabrics to produce four blend ratios of yarns beside 100% pure Giza 90 .It found that Giza 90 give better fiber length (mm),uniformity index(%), fiber strength (g/tex) and lower short fiber content as compared with card waste and recycled fabrics. 75% Giza 90 - 25% Recycled fibers gave better yarn strength and yarn evenness and yarn imperfections than the other blends .While, 33.3 % Giza 90 - 33.3% card waste - 33.3 recycled fabrics gave the lowest yarn strength and yarn evenness and yarn imperfections. Also, it found that Fiber and yarn quality properties of the blends improved as the ratio of Giza 90 increased in the blend. (Arafa 2019)

(Gadalla and Abdel Tawab 2019) reported that 100% Giza 95 give the highest upper half mean length, uniformity index, fiber strength, maturity ratio, reflectance degree and lea count strength product . On the other hand, the same variety recorded the lowest short fiber index, number of thin and thick places/100m and number of neps /100m.100% upland cotton gave the highest short fiber index, fiber elongation and micronaire value. Also, it found that increasing yarn count from 20s to 30s led to a significant increase in unevenness and yarn imperfections. While, lea count strength product was decreased with increasing yarn count from 20s to 30s .

(Abdel Ghaffer et al. 2019) found that increasing yarn count from 15s to 30s led to increase in yarn unevenness and yarn imperfections .while, yarn strength (cN/tex) and yarn hairiness were decreased with increasing yarn count .Also, it found that yarn count 30s give the highest yarn unevenness (CV%), number of thin places, thick places and neps/100m.

The investigation aimed to the influence of blending, with different percentages, on fiber and yarn properties. In addition, study the effect of blending ratio and yarn counts on mechanical and physical fiber and yarn quality properties to find out the optimum blending ratio that achieves the optimum yarn quality properties.

II. Materials and Methods

This study was carried out in the experimental cotton spinning mill, Cotton Research Institute. Egyptian commercial cotton variety Giza95 and upland cotton (Delta pine 245 cotton variety) were selected and blended with combed waste of Giza93extra-long staple to produce six different binary blend ratios of yarns beside prepared 100% pure Giza95 Egyptian cotton, 100% pure upland cotton and 100% combed waste. Blended samples were spun into 36s and 40s carded yarns spun at constant twist multiplier 4 on a ring spinning system. The ring spun yarn samples are presented in Table1.

Table 1. Ring spun yarns specifications

Blending code	Materials	Blending ratio
A	Giza 95 Egyptian cotton variety	100%
B	Upland cotton (Delta pine 245 cotton variety)	100%
C	Combed cotton waste of Giza93	100%
D	Giza95/ Delta pine 245	65% - 35%
E	Giza95 /Delta pine 245	35% - 65%
F	Giza95 / Combed cotton waste	65% - 35%
G	Giza95/ Combed cotton waste	35% - 65%
H	Delta pine 245 /Combed cotton waste	65% - 35%
I	Delta pine245 /Combed cotton waste	35% - 65%

Fiber and yarn tests were conducted in the laboratories of Cotton Technology Research Division, Cotton Research Institute, Agricultural Research Centre, Egypt. Fiber properties i.e. fiber length (UHM), uniformity index, short fiber index, fiber strength, fiber elongation, micronaire value, maturity ratio, fiber reflectance and fiber yellowness were measured on HVI according to (ASTM, D-5867-05) . Lea count strength product (LCSP) was performed on good brand (ASTM, D1578-93). Yarn strength and yarn elongation were measured in the laboratories of Textile Consolidation Fund on Uster Tensorapid4 (according to ASTM., D2256-02) at 5000 mm/min test speed and test length of 50cm used for the testing of tensile properties. Physical properties i.e. yarn evenness, yarn hairiness and yarn imperfection were examined on Uster Tester 3 at 400m/min test speed according to (ASTM, 1425-96) with testing speed of 400 mm/min. Mechanical yarn properties i.e. All samples were opened and left for 24 hours at least under the standard humidity and temperature conditions (65% ± 2% relative humidity and 21 ± 1°C temperature) before tested.

Statistical procedures

The experimental design was conducted as completely randomized design with four replications and analyzed as factorial experiment according to the method described by Gomez and Gomez (1984). Analysis of variance was carried out using SPSS 20.0 as a statistical program. The L.S.D. at 5% level of probability was used to calculate the significant differences between the mean values of treatments according to Snedecor and Cochran (1981).

III. Results and Discussion

1-Fiber quality properties:

Data in Table 2 and Fig 1 and 2 showed that significant differences between mean values of all fiber quality properties, i.e. upper half mean length, uniformity ratio, short fiber index, fiber strength, fiber elongation %, micronaire value, maturity ratio, color attributes (reflectance degree and yellowness) of Giza 95, Delta pine 245 cotton variety (*Gossypium hirsutum* L.), 100% combed waste and their blends. 100% Giza 95 cotton variety recorded higher mean values of upper half mean length (31.17 mm), uniformity ratio (86.77), fiber strength (36.97 g/tex), fiber elongation (8.23%) and maturity ratio (0.92 %) compared with 100% Delta pine 245 cotton variety, 100% combed waste and all blends. On the other hand , 100% Delta pine 245 cotton variety gave the lowest mean values of upper half mean length (27.03 mm) , uniformity ratio (81.43) , fiber strength (27.27g/tex) , maturity ratio (0.84%) and yellowness (8.53). While the same variety recorded the highest mean value of micronaire value (4.97). Regarding the different blends, 65% Giza95-35% combed waste gave better mean values of upper half mean length (29.97 mm), uniformity ratio (84.90), fiber strength (35.23 g/tex), maturity ratio (0.91 %) and yellowness (11.67) as compared to 100% Delta pine 245 cotton variety, 100% combed waste and all different blends. These results are in harmony with

those reported by (Mabrouk and Nour 2005 ;Arafa 2019) who reported that increasing the portion of Giza 90 fibers in the blended led to increase in fiber length, uniformity index ,fiber strength and decrease short fiber index.

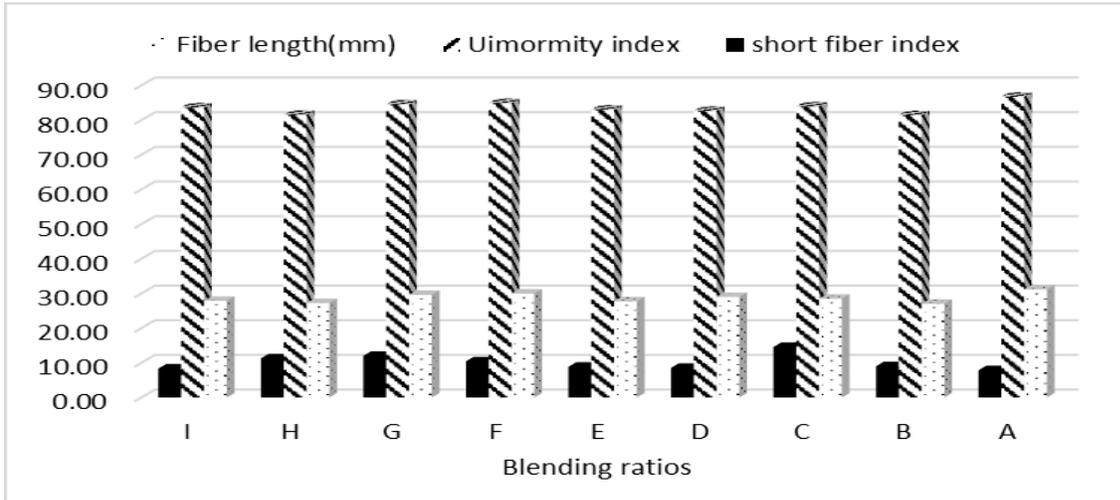


Fig.1.Fiber length, uniformity index and short fiber index for Giza95, Delta pine 245, combed waste fibers and their blends

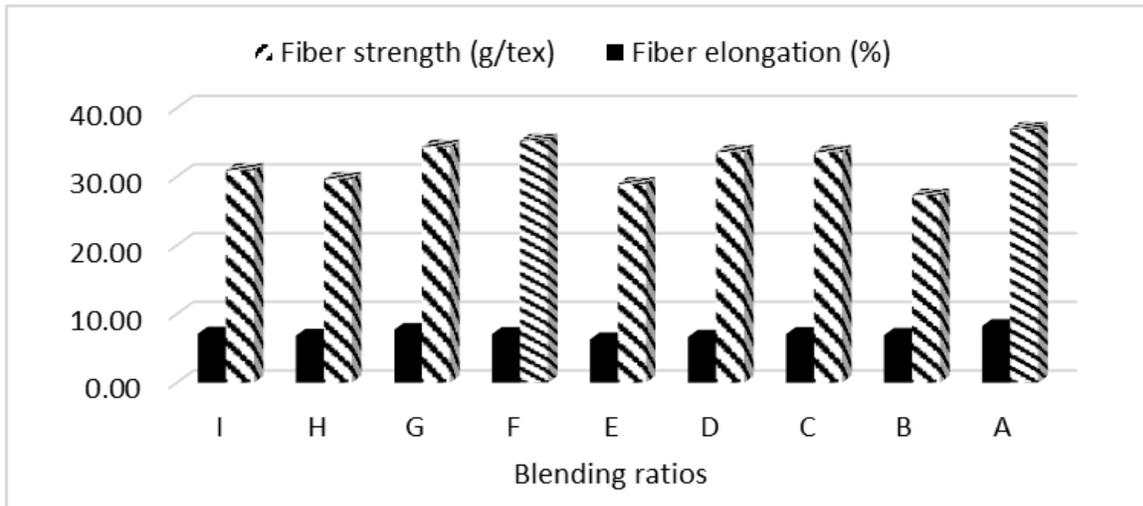


Fig.2.Fiber strength (g/tex) and fiber elongation (%) for Giza95, Delta pine 245, combed waste fibers and their blends

Table 2.Effect of blending cotton materials on fiber quality properties and color attribute as estimated by (HVI)

Materials	UHML (mm)	Uniformity (%)	SFI (%)	Fiber Strength (g/tex)	Fiber elongation (%)	Micronaire value	Maturity ratio	Color Attribute	
								RD	+b
100 % pure Giza 95 cotton	31.17	86.77	7.87	36.97	8.23	4.73	0.92	68.33	11.57
100 % pure Upland cotton (Delta Pine 245)	27.03	81.43	9.03	27.27	6.93	4.97	0.84	68.50	8.53
100 % Combed cotton waste	28.47	83.97	14.57	33.57	7.07	3.70	0.89	73.67	11.63
65% Giza 95-35% Delta Pine 245	28.99	82.67	8.53	33.60	6.67	4.60	0.88	69.67	11.53
35% Giza 95-65% Delta Pine 245	27.73	83.03	8.87	28.93	6.30	4.90	0.87	68.27	9.67
65% Giza 95- 35% Combed cotton waste	29.97	84.90	10.43	35.23	7.07	4.50	0.91	68.23	11.67
35% Giza 95- 65% Combed cotton waste	29.60	84.53	12.03	34.37	7.67	4.10	0.90	71.43	11.60
65% Delta Pine 245- 35% Combed cotton waste	27.23	81.50	11.30	29.67	6.83	4.37	0.85	74.40	10.07
35% Delta Pine 245-65% Combed cotton waste	27.87	83.67	8.37	30.93	7.13	4.17	0.88	73.50	9.53
LSD at 0.05	0.60	0.36	4.16	0.56	0.34	0.23	0.05	0.51	0.57

High Volume Instrument (HVI), Upper half means length (UHML), Short fiber index (SFI %), reflectance degree (RD %), Fiber yellowness degree (b+)

2. Yarn quality properties

2.1. Mechanical yarn properties

Mechanical yarn properties of ring spun cotton blended yarns are given in Table 3 and Fig 3 and 4 .The effect of blending ratio and its components were highly significant on lea count strength product (LCSP), yarn strength and yarn elongation of ring spun cotton blended yarns. Lea count strength product (2365), yarn strength (19.36 cN/tex) and yarn elongation (5.79 %) of 100% Giza95 cotton yarn were more than 100% Delta pine 245 cotton variety, 100% combed cotton waste and the other blended yarns. 65% Giza95-35% combed waste of blended yarns give better lea count strength product (2285), yarn strength (18.91 cN/tex) and yarn elongation (5.47%) compared with all blended yarns and 100% Delta pine 245 cotton variety and 100% combed cotton waste. Followed by 35% Giza95- 65% combed waste .While, 65% Delta pine 245 -35% combed waste cotton blended yarn gave lower lea count strength product, yarn strength and yarn elongation than all blended yarns. It noticed that mechanical yarn properties increased as the proportion of Giza95 cotton variety increased in blended yarns.

Table 3.Mechanical yarn properties for ring blended yarns

Blending code	Materials	Lea count strength product	Yarn strength (cN/tex)	Yarn elongation (%)
A	100 % pure Giza 95 cotton	2365	19.36	5.79
B	100 % pure Upland cotton (Delta Pine 245)	1555	14.31	3.56
C	100 % Combed cotton waste	1815	16.66	4.18
D	65% Giza 95-35% Delta Pine 245	1800	16.75	4.71
E	35% Giza 95-65% Delta Pine 245	1695	15.34	4.07
F	65% Giza 95- 35% Combed cotton waste	2285	18.91	5.47
G	35% Giza 95-65% Combed cotton waste	2020	17.81	4.39
H	65% Delta Pine 245- 35% Combed cotton waste	1690	15.31	3.95
I	35% Delta Pine 245- 65% Combed cotton waste	1780	16.42	4.13
LSD at 5%		57.69	0.09	0.09

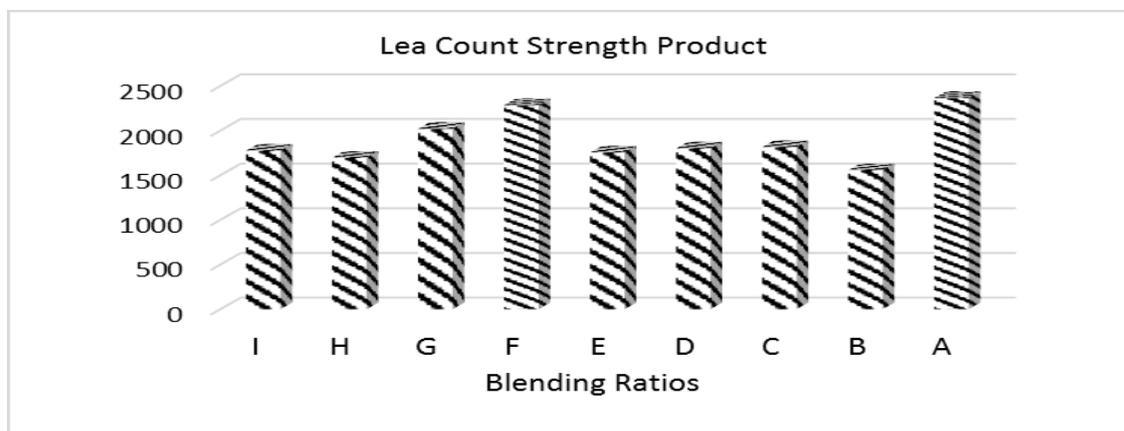


Fig.3. Lea count strength product of ring spun cotton blended yarns

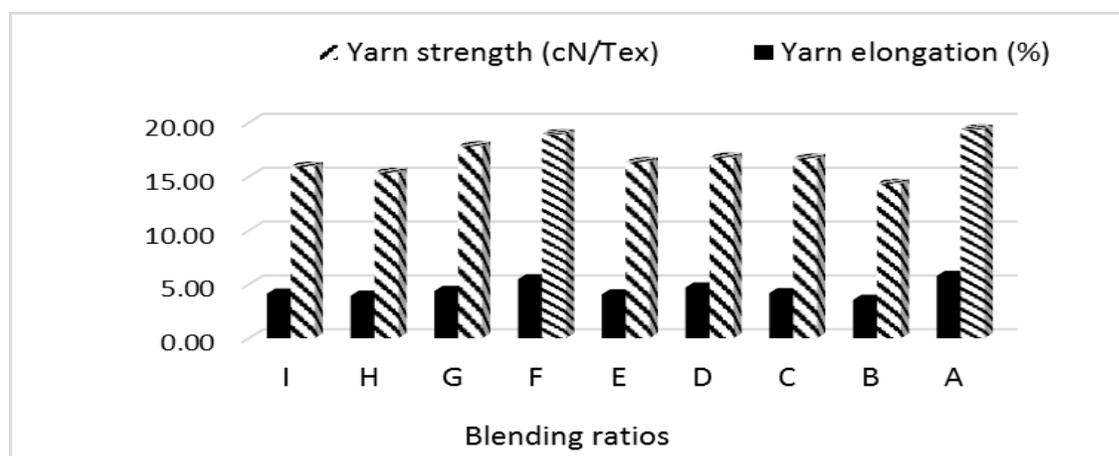


Fig.4. Yarn strength (cN/tex) and yarn elongation (%) of ring spun cotton blended yarns

As shown in Table 4 and Fig 5 and 6 yarn count had significant effect on all mechanical yarn properties. Also, it found that yarn count 36s gave higher lea count strength product, yarn strength and yarn elongation than yarn count 40s. It noticed that increasing yarn count from 36s to 40s led to decrease lea count strength from 1921 to 1875, yarn strength from 17.04 to 16.61 cN/tex and yarn elongation from 4.58 to 4.37%. These results are agree with (Sanad et al. 2011; Abd-Elkawe and El-Sayed 2021) who reported that yarn strength (cN/tex) was decreased with increasing yarn count that may be due to the lower number of fibers in cross section of fine yarns.

Table 4. Effect of yarn count on mechanical yarn properties

Mechanical yarn properties	Yarn count		LSD at 0.05
	36s	40s	
lea count strength product	1921	1875	**
Yarn strength (cN/tex)	17.04	16.61	**
Yarn elongation (%)	4.58	4.37	*

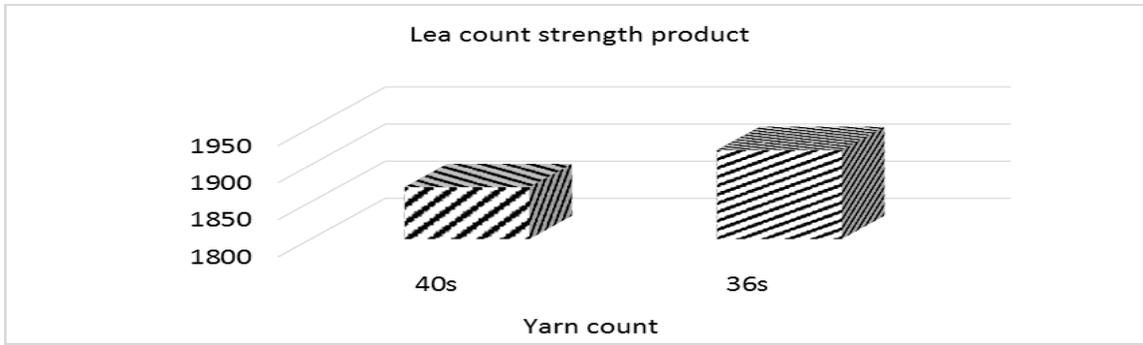


Fig.5. Lea count strength product for ring spun blended yarns at 36s and 40s yarn counts

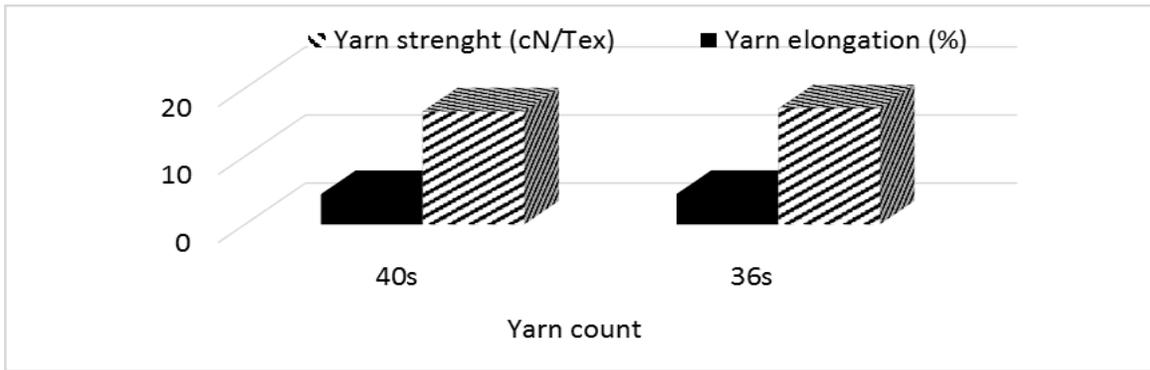


Fig.6. Yarn strength and yarn elongation for ring spun blended yarns at 36s and 40s yarn counts

Regarding data in Table 5 and Fig 7 showed that the interaction between blending ratio and yarn count had significant effect on all mechanical yarn properties except lea count strength product. 65% Giza95-35% Combed waste blended yarn spun into 36s yarn count give better yarn strength (19.12 cN/tex) and yarn elongation (5.58%) as compared with all blended yarns. While, 100% Delta pine 245 recorded the lowest yarn strength and yarn elongation. Also, 65% Delta pine 245– 35% combed waste blended yarn at 40s yarn count gave lower yarn strength (15.21 cN/tex) and yarn elongation (3.92 %) than all blended yarns.

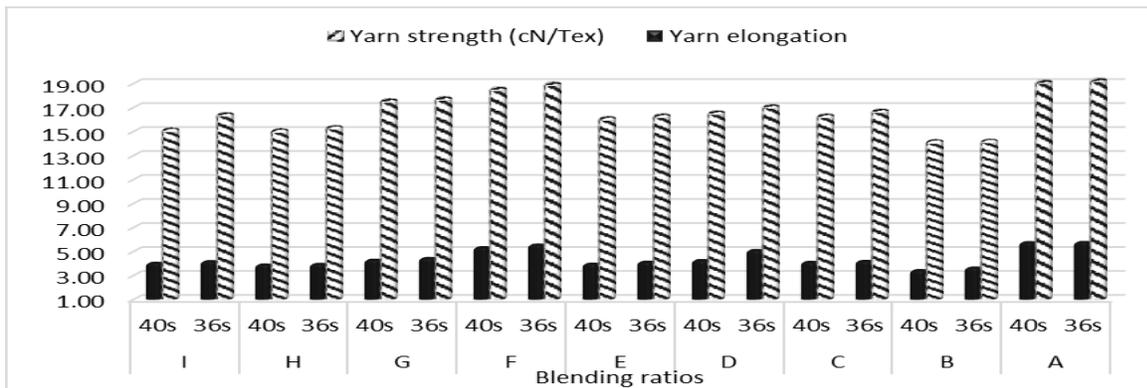


Fig.7. Yarn strength (cN/tex) and yarn elongation (%) for ring spun blended yarns at different yarn counts

Table 5. Lea count strength product, yarn strength and yarn elongation for ring spun yarns as affected by the interaction between blending ratio and yarn count

Blending code	Materials	Yarn count	Lea count strengt h	Yarn strength cN/tex	Yarn elongation (%)
A	100 % pure Giza 95 cotton	36s	2385	19.44	5.80
		40s	2347	19.29	5.78
B	100 % pure Upland cotton (Delta Pine 245)	36s	1567	14.33	3.67
		40s	1542	14.29	3.46
C	100 % Combed cotton waste	36s	1847	16.86	4.22
		40s	1782	16.45	4.14
D	65% Giza 95-35% Delta Pine 245	36s	1855	17.23	5.13
		40s	1773	16.71	4.29
E	35% Giza 95-65% Delta Pine 245	36s	1767	16.45	4.15
		40s	1745	16.23	3.99
F	65% Giza 95- 35% Combed cotton waste	36s	2312	19.12	5.58
		40s	2257	18.71	5.37
G	35% Giza 95- 65% Combed cotton waste	36s	2053	17.90	4.46
		40s	1990	17.73	4.32
H	65% Delta Pine 245- 35% Combed cotton waste	36s	1707	15.47	3.97
		40s	1687	15.21	3.92
I	35% Delta Pine 245- 65% Combed cotton waste	36s	1798	16.56	4.20
		40s	1752	15.27	4.07
LSD at 5%			NS	0.139	0.128

2.2 Physical yarn properties

Data in Table 6 showed the effect of blending ratios on Physical yarn properties of ring spun cotton blended yarns. Results indicated that blending ratio had significant effect on thin places, thick places, neps, unevenness (%) and yarn hairiness of ring spun cotton blended yarns. Thin places (119), thick places (215) , neps (114), unevenness (19.76) and yarn hairiness (3.92) of 100% Giza 95 cotton yarn were lower than 100% Delta pine 245 variety, 100% combed waste and the other blended yarns. While, 100% Delta pine245 recorded the highest thin places (444), thick places (573), neps (421), unevenness (23.50) and yarn hairiness (5.75). 65% Giza95-35% combed waste of blended yarns give better thin places (139), thick places (250), neps (171), unevenness (20.29) and yarn hairiness (4.30) compared with all blended yarns and 100% upland cotton Delta pine 245 variety and 100% combed waste followed by 65% combed waste - 35% Giza95. On the other hand, 65% Delta pine245- 35% combed waste gave higher thin places (400), thick places (514), neps (390), unevenness (22.44) and yarn hairiness (5.40) than all blended yarns. It observed that yarn imperfections and yarn hairiness increased with increasing proportion of Delta pine 245 cotton variety in blended yarns. Yarn Unevenness increased with decreasing fiber length and increasing short fiber content (Wali 2003).

Table 6.Physical yarn properties for ring blended yarns

Blending code	Materials	Thin (-50)	Thick (+50)	Neps (+200)	Unevenness (CV %)	Hairiness
A	100 % pure Giza 95 cotton	119	215	114	19.76	3.92
B	100 % pure Upland cotton (Delta Pine 245)	444	573	421	23.50	5.75
C	100 % Combed cotton waste	328	440	326	21.65	4.97
D	65% Giza 95-35% Delta Pine 245	283	414	275	21.02	4.72
E	35% Giza 95-65% Delta Pine 245	399	506	381	22.28	5.31
F	65% Giza 95- 35% Combed cotton waste	139	250	171	20.29	4.30
G	35% Giza 95- 65% Combed cotton waste	236	370	220	20.68	4.35
H	65% Delta Pine 245- 35% Combed cotton waste	400	514	390	22.44	5.40
I	35% Delta Pine 245-65% Combed cotton waste	361	471	344	21.93	5.14
LSD at 0.05		21.79	15.66	14.60	0.189	0.123

Data presented in Table 7 and Fig 8 and 9 showed that yarn count had significant effect on yarn imperfections and yarn hairiness. Yarn count 40s recorded higher thin places (315), thick places (429), yarn unevenness (21.73), number of neps (306) and yarn hairiness (4.98) than 36s yarn count. It observed that yarn unevenness (CV %), the number of thin and thick places were increased with increasing yarn count.

Table 7. Effect of yarn count on physical yarn properties

Physical yarn properties	Yarn count		LSD at 5%
	36s	40s	
Thin places (-50%)	290	315	**
Thick places (+50%)	404	429	**
Neps (+200%)	281	306	**
Unevenness (CV %)	21.28	21.73	*
Hairiness	4.76	4.98	*

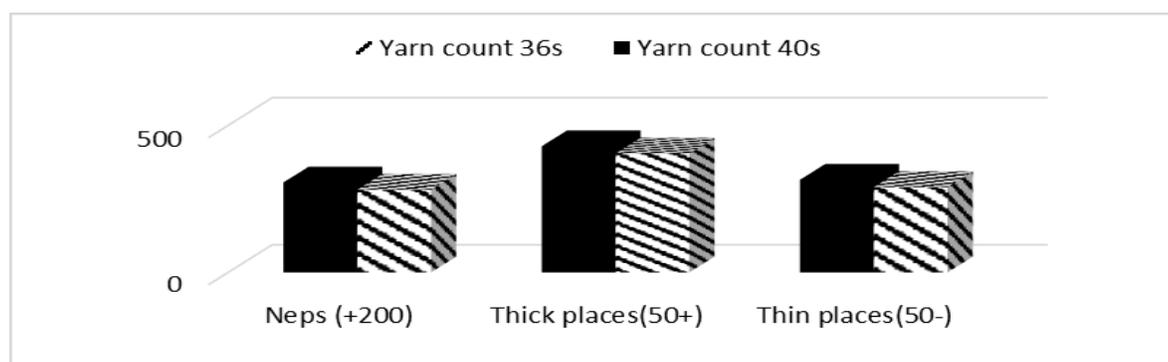


Fig.8 Number of neps, thin and thick places at different yarn counts

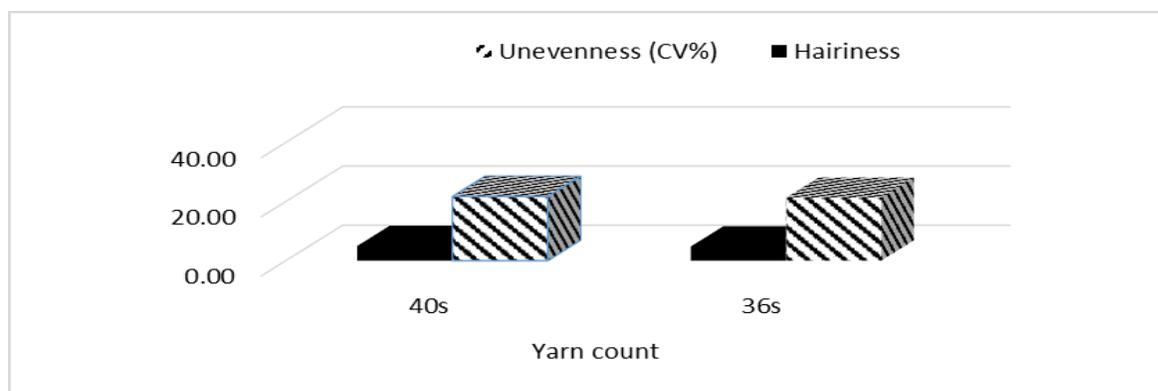


Fig.9. Yarn unevenness (CV %) and yarn hairiness at different yarn counts

As shown in Table 8 and Fig.10 showed that the interaction between blending ratio and yarn count had significant effect on all physical properties except thin and thick places. Giza95 cotton variety at 36s yarn count give the best imperfections and yarn hairiness than 100% Delta pine 245 cotton yarn, 100% combed waste and all blended yarns. 65% Giza95-35% combed waste of ring yarn spun into 36s yarn count give better number of neps (164) , unevenness (20.09) and yarn hairiness (4.08) as compared with all blended yarns. On the other hand, 65% Delta pine - 35% waste of ring yarn spun into 40s yarn count recorded highest number of neps, unevenness and yarn hairiness than all blended yarns. These results are in agreement with those obtained by (Arafa 2009; Abd-Elkawe and El-Sayed 2021) who stated that yarn count had significant effect on yarn strength, unevenness and yarn imperfections. It cleared that 65% Giza95-35% combed waste was the optimum blending ratio that achieves the optimum yarn quality properties.

Table 8. Effect of the interaction between blending ratio and yarn count on yarn imperfections and hairiness yarn

Materials	Yarn count	Thin (50-)	Thick (50+)	Neps (200+)	CV %	Hairiness
100% Giza95	36s	92	195	94	19.11	3.84
	40s	145	235	134	20.40	4.00
100% Delta pine 245	36s	434	555	412	23.23	5.58
	40s	454	590	431	23.77	5.92
100% Combed waste	36s	320	424	298	21.44	4.85
	40s	336	456	354	21.86	5.08
65% Giza95 - 35% Delta pine	36s	262	395	264	20.84	4.48
	40s	304	433	287	21.19	4.96
35% Giza95 -65% Delta pine	36s	393	493	374	22.13	5.31
	40s	404	518	389	22.44	5.31
65% Giza95- 35% waste	36s	131	236	164	20.09	4.08
	40s	146	263	178	20.49	4.51
35% Giza95- 65% waste	36s	226	366	211	20.51	4.30
	40s	246	374	229	20.84	4.41
65% Delta pine -35% waste	36s	408	508	388	22.35	5.36
	40s	427	520	392	22.53	5.44
35% Delta pine -65% waste	36s	346	467	329	21.77	5.07
	40s	375	474	360	22.08	5.20
LSD at 5%		NS	NS	20.66	0.27	0.17

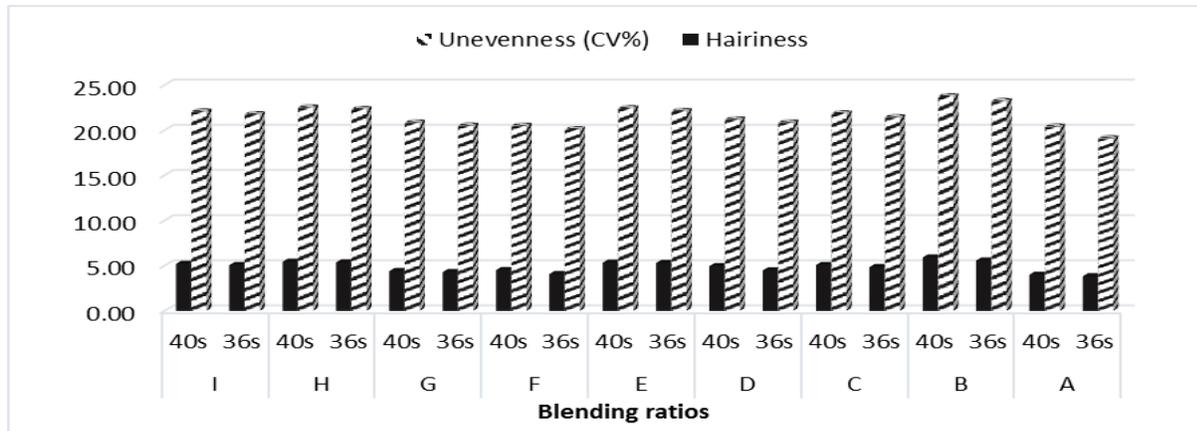


Fig.10. Yarn Unevenness and yarn hairiness for blended yarns at two yarn counts

IV. Conclusion

Recycling waste materials is very important and necessary process because it reduces the production costs, decreases the harmful impacts on environment, produces new textile products. The purpose of this investigation was to study the influence of blending ratios and its components and yarn count on fiber and yarn quality properties. Yarn count and blending ratios had significant effect on the most yarn properties. Yarn hairiness, yarn unevenness and yarn imperfection increased with increasing yarn count from 36s to 40s. While,lea count strength product, yarn strength and yarn elongation decreased with increasing yarn count. Also, increasing the proportion of upland fibers in blended yarns led to decrease yarn strength, lea count strength and yarn elongation and increase unevenness and hairiness due to increase the amount of short fiber in blended yarn. 65% Giza95-35% combed waste was the optimum blending ratio that achieves the optimum yarn quality properties. Increasing proportion of G95 cotton variety in blended samples led to improve fiber, mechanical and physical yarn properties.

References

- [1]. Abd-Elkawe, E.Y. and El-Sayed, E.R. (2021) .Production of Fine Count Yarns from Some Extra-long Egyptian Cottons on Different Spinning Systems. *European Journal of Agriculture and Food Sciences*.3 (5):90-96.
- [2]. Abdel Gaffar F. E., Hammam, G.Y.M. , El- Hosary A.A.A., El- Gedwy, E.M.M., Hassan, A.A.(2019) Influence of some commercial blends between the imported cotton and the upper Egyptian varieties on technological properties," *Annals of Agricultural Science, Moshtohor*, 57(1):.31 – 38.
- [3]. Arafa H. M. (2009) .Comparative study on spinning potential and yarn quality of promising crosses and some Egyptian cotton cultivars. Ph.D, Thesis, Fac. of Agric. Cairo Univ., Egypt.
- [4]. Arafa H. M. (2019). Producing yarns from blends of card wastes, recycled fabric and medium quality cotton. *Bull. Fac . Agric., Cairo Univ.*, 70: 453-460
- [5]. ASTM (1993). American Society for Testing and Materials.Standards of Textile Testing and Materials. (D 1578 -93). USA.
- [6]. ASTM (1996). American Society for Testing and Materials.Standards of Textile Testing and Materials, Philadelphia, Pa. (D1425-96).USA.
- [7]. ASTM (2002). American Society for Testing and Materials.Standards of Textile Testing and Materials. (D 2256 -02). USA.
- [8]. ASTM (2005). American Society for Testing and Materials.Standards of Textile Testing and Materials. (D 5867 -05). USA.
- [9]. Bhardwaj, S and Juneja, S. (2012). Performance of Jute Viscose/Polyester and Cotton Blended: Yarns for Apparel Use. *Stud Home Com Sci*, 6 (1): 33-38
- [10]. Bhatia, D., Sharma, A. and Malhotra, U. (2014).Recycled fibers: An overview .*International Journal of Fiber and Textile Research*.4 (4):77-82.

- [11]. Charankar, S.P., Verma, V., Gupta, M. and Nanavati B.M., (2007) Journal of the Textile Association, **67**(5): 201.
- [12]. Cierpucha , W. Czaplicki, Z. Mankowski, J. Kolodziej, J. Zareba, S. and Szporek, J. (2006) Fibers & Textile in Eastern Europe,14(5)80.
- [13]. Gadalla, A.E.M. and R.M. Abdel-Tawab. (2019). Effect of blending treatments between upland cotton (*Gossypium hirsutum L.*) and Giza95 cultivar (*Gossypium barbadense L.*) on fiber and yarn quality. Bull. Fac. Agric., Cairo Univ., 70 (4): 351-361.
- [14]. Gomez, K. A. and Gomez, A. A. (1984) Statistical procedures for agricultural research 2nd ed. John Wiley and Sons, New York, USA. 680.
- [15]. Khan, M.K.R., Sarker, R.C. and Rahman H. (2015). The influence of some process parameters on rotor spun yarn quality produced from recycled cotton spinning wastes. Int'l J. Textile Sci., 4(1): 9-19.
- [16]. Langenhove V.S. (2002). Optimising the fiber-to yarn Production process: Finding a blend of fiber qualities to create an optimal Price/quality yarn. Autex Research Journal 2 (5): 57-63.
- [17]. Mabrouk , K.I.K. and Nour, M.O.D. (2005) .Possibility of spinning and blending the waste of carding and combing for coarse count on the open- end rotor spinning .Egypt Agric.Res.,83(3):1305-1315.
- [18]. Marinus H.J. (2007). Blending could add value to long staple upland varieties, Textile and Fiber Technology. The Australian Cotton Grower, 34-38.
- [19]. Mohamed ,A.M.M and El-Bagoury ((2005) Outlook of the Egyptian contemporary cotton spinning industry. the 1st Euro –Mediterranean Textile & Clothing Supply Chain Integration Conference.9th to 11th May .Cairo. Egypt
- [20]. Rajalakshmi M., Koushik C.V. and Prakash C. (2012) Journal of Textile Science and Engineering.2 (6)1
- [21]. Rizk, M.A.M., Azab, A.M., Emesbah, E.A. Hassan, A.A and Yonis, M.A.(2016)Technological study on some yarn properties of extra-long staple in Egyptian cotton varieties .Al-Azhar. J. Agric. Res., 26:570-577.
- [22]. Saha, S. K., Jamal, H. and Masudur, R. A.N.M. (2020) Effect of blend ratio on cotton-modal fiber blended ring-spun yarn quality with varying modal fiber percentage. Journal of Textile Science & Engineering Research Article. 10(1).
- [23]. Sanad, S.H. Mahmoud H.E.M. and El-Sayed, M.A.M. (2011) Production of carded compact cotton yarn of comparable quality to the combed conventional ring yarn,” Egypt J Agric Res, Vol. 89, no.1, pp. 203-212, 2011.
- [24]. Sharma R. and Joel A. (2017). Development of nonwoven fabric from recycled fibers. J Textile Sci. Eng., 7(2): 1-3.
- [25]. Snedecor and Cochran (1981). Statistical methods 7th ed. Iowa State Univ. Press Ames, Iowa.
- [26]. Wali, A.M. (2003). Effect of cotton fiber properties on yarn quality. M.Sc. Thesis, Fac. Agric., Saba Basha, Alex. Univ., Egypt.
- [27]. Wang, Y. (2010) Fiber and Textile Waste Utilization, Waste Biomass Valor, 1:135–143.

Eman Rashwan El – Sayed, et. al. “Effect of the blending between upland and combing waste on cotton fiber and yarn quality.” *IOSR Journal of Polymer and Textile Engineering (IOSR-JPTE)*, 09(04), 2022, pp. 34-45.